

DAP™-AM Series

Daido Alloy Powder – for Additive Manufacturing

SUS420J2

The metal powders with high flowability suitable for additive manufacturing by SLM

Characteristics

Martensitic stainless steel powder with high strength and hardness obtained by quenching and tempering.

Major applications

Plastic injection molds

Typical chemical composition and hardness

Typical Chemical composition(mass%)				Hardness(HRC)
C	Si	Mn	Cr	Annealing : 32-35HRC
0.33	0.6	0.4	13	Tempering after quenching : 50-53HRC

Particle size

Particle size(μm)
-53/+25

Characteristics

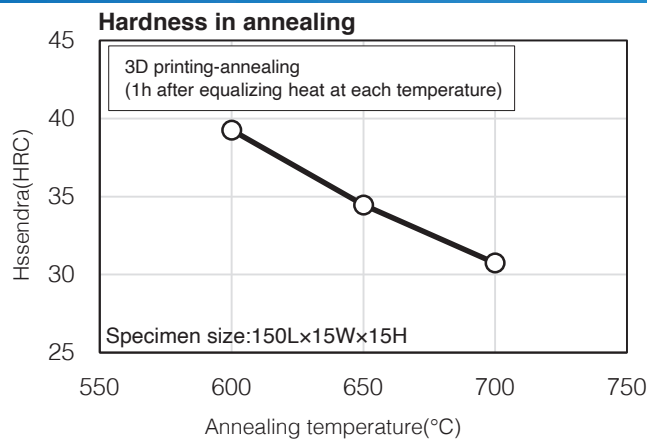


Fig.1 Relationship between annealing temperature and hardness of a 3D-printed sample

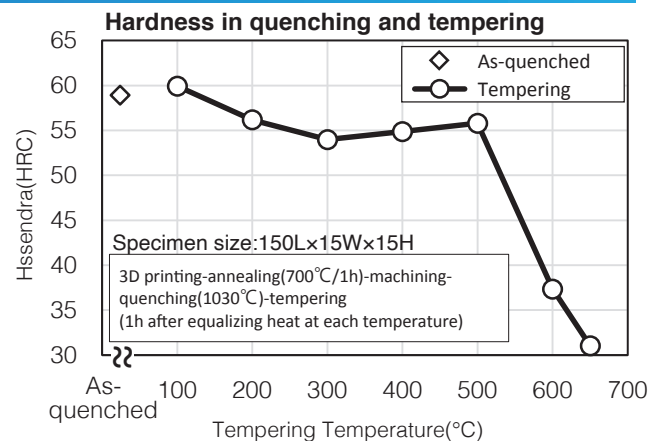


Fig.2 Relationship between tempering temperature and hardness of a 3D-printed sample

Tensile properties and Charpy impact value

Heat treatment	Hardness (HRC)	YS (MPa)	TS (MPa)	Elongation (%)	Reduction of area (%)	Charpy impact value (J/cm ²)
Annealing *3	34	901	1142	17	52	65
Tempering *4	53	1637	1963	10	24	30

*1 Tested temperature : RT, Tested specimen : JIS No.14A, Gauge length : 25mm, Parallel area diameter : φ5mm, Testing method : JIS Z 2241-2011 Standard

*2 Tested specimen: JIS No.3 (2mm U-notch)

*3 Detail process : 3D printing-Removing from base plate-annealing-Precision machining

*4 Detail process : 3D printing-Removing from base plate-annealing-Machining-Quenching(1030°C)-Tempering-Precision machining



Tokyo Head Office Daido Shinagawa Building, 6-35, Konan 1-chome, Minato-ku, Tokyo, 108-8478 TEL +81-3-5495-1284
(Metal Powder Marketing & Sales Sect. Metal Powder Dept.)

Nagoya Office 10, Ryugu-cho, Minato-ku, Nagoya, Aichi, 455-0022 TEL +81-52-694-0776

Web site: <https://www.daido.co.jp/en/products/powder/index.html> Email address: funmatsu@ask.daido.co.jp

DAP is a trademark or a registered trademark of Daido Steel Co., Ltd.

Disclaimer and copyright

The figures in this document are typical values based on the results of our tests and there is no guarantee that the figures presented will be achieved when the products are used. The information in this document is subject to change without notice. Please contact us for the latest information. Any unauthorized distribution or reproduction of the content of this document is prohibited.